

A note on the Winterbottom shape

Leonard Kreutz 

School of Computation, Information and Technology, Technical
University of Munich, Boltzmannstraße 3, 85748 Garching bei München,
Bavarn, Germany (leonard.kreutz@tum.de) (corresponding author)

Bernd Schmidt

Institut für Mathematik, Universität Augsburg, Universitätsstr. 14,
86159 Augsburg, Bayern, Germany
(bernd.schmidt@math.uni-augsburg.de)

(Received 9 February 2024; revised 23 July 2024; accepted 5 August 2024)

In this short note, we review results on equilibrium shapes of minimizers to the sessile drop problem. More precisely, we study the Winterbottom problem and prove that the Winterbottom shape is indeed optimal. The arguments presented here are based on relaxation and the (anisotropic) isoperimetric inequality.

Keywords: capillarity problems; crystallization; dewetting; interfacial energies; wetting; Winterbottom shape

2010 *Mathematics Subject Classification:* Primary: 49Q20
Secondary: 35A15; 82B24

1. Introduction

For solid crystals with sufficiently small grains, Herring [12] claims that the bulk contribution to their configurational energy is negligible with respect to the surface tension. Thus, in this setting, when determining the equilibrium shape of a crystal, interfacial energies of the type

$$P_{\varphi}(E) = \int_{\partial^* E} \varphi(\nu_E) \, d\mathcal{H}^{d-1}$$

play a fundamental role. Here, $\varphi: \mathbb{R}^d \rightarrow [0, +\infty)$ is a convex and positively homogeneous function of degree one that describes the possibly anisotropic surface tension of the crystal. The set E is assumed to be sufficiently regular (i.e., E is a set of finite perimeter), $\partial^* E$ denotes its (measure theoretic) boundary, and $\nu_E(x)$ the outer normal to the set E at the point $x \in \partial^* E$. The Wulff problem consists in studying solutions of

© The Author(s), 2024. Published by Cambridge University Press on behalf of The Royal Society of Edinburgh. This is an Open Access article, distributed under the terms of the Creative Commons Attribution licence (<https://creativecommons.org/licenses/by/4.0/>), which permits unrestricted re-use, distribution, and reproduction in any medium, provided the original work is properly cited.

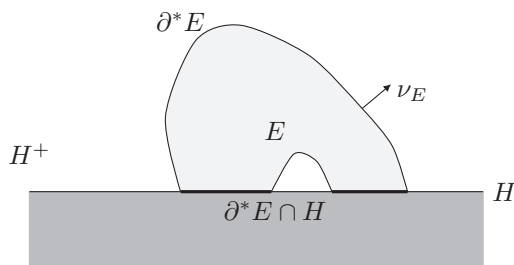


Figure 1. A generic configuration admissible for (1.4). The substrate is illustrated in dark grey, the region occupied by the crystal is illustrated in light grey, and the contact surface is illustrated in as a thick line.

$$E \in \operatorname{argmin} \{P_\varphi(E) : |E| = v\}, \quad (1.1)$$

where $v > 0$ is given. This problem is an anisotropic generalization of the classical isoperimetric problem. In the early 1900s, Wulff [20] proposed a geometric construction to (1.1) given by

$$W_\varphi = \{x \in \mathbb{R}^d : x \cdot \nu \leq \varphi(\nu) \text{ for all } \nu \in \mathbb{S}^{d-1}\}. \quad (1.2)$$

This shape is nowadays known as the Wulff set (or Wulff crystal) of φ . Dinghas proved formally in [6] that among convex polyhedra the Wulff set is the shape having the least surface integral for the volume it contains. The proof has later been rendered precise by Taylor [16–18] using arguments from geometric measure theory.

The Wulff variational problem provides a description of an equilibrium crystal shape deep inside a region in the gas phase. This leads to the natural question whether, likewise, it is possible to determine the shape of a crystal growing on a substrate that minimizes a suitable combination of its surface tension and the interaction energy with the substrate. Such a situation may be described as follows. For φ as above and $\lambda \in \mathbb{R}$, we set

$$F_{\lambda, \varphi}(E) = \int_{\partial^* E \cap H^+} \varphi(\nu_E) \, d\mathcal{H}^{d-1} + \lambda \mathcal{H}^{d-1}(\partial^* E \cap H), \quad (1.3)$$

where $H^+ = \{x \in \mathbb{R}^d : x_d > 0\}$, $H = \{x \in \mathbb{R}^d : x_d = 0\}$ and E is a set of finite perimeter in H^+ , i.e. $|E \setminus H^+| = 0$, which we simply denote by $E \subseteq H^+$, cf. figure 1. Here, as in the Wulff problem, φ represents the (anisotropic) surface tension density between crystal and vapour and $\lambda \in \mathbb{R}$ is the relative adhesion coefficient between the crystal and the substrate (i.e., the difference of the crystal-substrate and the substrate-vapour interfacial energy per unit surface area). In this setting,

the Winterbottom problem [19] consists in studying the existence and finding the solutions of

$$E \in \operatorname{argmin} \{F_{\lambda,\varphi}(E) : E \subseteq H^+, |E| = v\}, \quad (1.4)$$

where $v > 0$. There are three interesting parameter regimes to consider (see [remark 4](#)):

- (1) If $\lambda \geq \varphi(-e_d)$ it is energetically inconvenient for the crystal to attach to the substrate and therefore the solution (1.4) coincides (up to translation) with the solution of (1.1). This phenomenon is called complete drying.
- (2) If $\lambda \in (-\varphi(e_d), \varphi(-e_d))$ a solution to the Winterbottom exists, but its shape differs from the Wulff shape given in (1.2). In fact, the solution shape is now the Winterbottom shape given by

$$W_{\lambda,\varphi} = W_\varphi \cap \{x \in \mathbb{R}^d : x_d \geq -\lambda\} \quad (1.5)$$

suitably rescaled and placed in order to be in contact with the substrate. In this case, we speak of partial drying/wetting.

- (3) If $\lambda \leq -\varphi(e_d)$ complete wetting occurs: It is energetically favourable to create large surface area in common with the substrate. This allows to create arbitrarily small energy (if $\lambda = -\varphi(e_d)$) or even energy diverging to $-\infty$ (if $\lambda < -\varphi(e_d)$).

We rigorously study all the cases. From the point of view of the mathematical analysis, the most interesting regime to consider is the partial wetting regime (2). There, our first main result [theorem 3](#) proves that indeed (1.5) solves (1.4).

In the case where φ is smooth, the solution given in (1.5) in particular recovers Young's law [21]. This law relates the contact angle of the boundary of equilibrium configurations with the adhesion coefficient λ . More precisely, if $\partial(\overline{E} \cap H)$ denotes the boundary of $\overline{E} \cap H$ in H , then

$$\nabla \varphi(\nu_E(x)) \cdot (-e_d) = \lambda, \quad \text{for all } x \in \partial(\overline{E} \cap H) \quad (1.6)$$

(see [remark 4\(v\)](#)). In the isotropic case, i.e., $\varphi(\nu) = |\nu|$, this reads (cf. [figure 2](#))

$$\nu_E(x) \cdot (-e_d) = \lambda, \quad \text{for all } x \in \partial(\overline{E} \cap H).$$

The equilibrium condition (1.6) has been derived more generally for anisotropic capillarity problems in [5] and for epitaxially strained thin films in [4].

The proof that (1.5) is the solution shape to (1.4) provides a rigorous justification of an ansatz that has been previously considered in [14]. It essentially relies on the anisotropic isoperimetric inequality [7] for the case $\lambda > 0$ and change of coordinates in the case that $\lambda \leq 0$. In particular, the quantitative isoperimetric inequality [3, 8, 11] implies the stability of the Winterbottom shape. The stability of the Winterbottom shape has already been proved in two dimensions in [14] with the use of the (generalized) Bonnesen inequalities [2]. The stability of the Winterbottom shape in any dimension is the content of our second main result, [theorem 5](#): For a

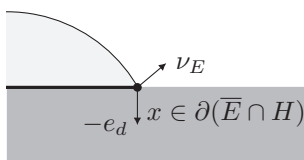


Figure 2. Young's law for the contact angle. ν_E is the normal at the point $x \in \partial(\overline{E} \cap H)$ and $-e_d$ is the normal vector of H pointing outwards with respect to the region the crystal may occupy.

set $E \subset H^+$, we show that its squared asymmetry index (i.e., the Lebesgue measure of the symmetric difference of E with the optimally placed Winterbottom shape of equal volume) is controlled by the isoperimetric difference (the energy deficit of E and the Winterbottom shape).

The article is organized as follows. In §2, we introduce the problems, discuss the different parameter regimes, and state the main theorems. In §3, we prove the main theorem. Here, we would like to point out that, due to the presence of substrate, we are working with discontinuous integrands in general and thus, some of the results already present for continuous integrands need to be proved again in our setting, cf. [proposition 2](#).

Finally, we mention the articles [13] and [15] on this topic, which—independently of our contribution—were published on arxiv.org at essentially the same time.

2. Settings and main results

Notation and preliminaries

For a measurable subset B of \mathbb{R}^d , we denote by $|B|$ its d -dimensional Lebesgue measure and by $\mathcal{H}^k(B)$ its k -dimensional Hausdorff measure. Given $x, y \in \mathbb{R}^d$, we denote by $x \cdot y$ their scalar product and by $\|x\|$ the Euclidean norm of x . For $r > 0$, $x \in \mathbb{R}^d$ we write $B_r(x) = \{y \in \mathbb{R}^d : \|y - x\| < r\}$ and abbreviate $\mathbb{S}^{d-1} = \partial B_1(0)$. We also introduce the half space $H^+ = \{x \in \mathbb{R}^d : x_d > 0\}$ and the hyperplane $H = \{x \in \mathbb{R}^d : x_d = 0\}$. If $E \subset \mathbb{R}^d$ is a set of finite perimeter (i.e., its characteristic function is of bounded variation), we write $\partial^* E$ for the reduced boundary of E and denote by $\nu_E : \partial^* E \rightarrow \mathbb{S}^{d-1}$ the generalized outer normal to E . We refer to [1] for the definition of these objects and basic facts about sets of finite perimeter. In particular, if $K \subseteq \mathbb{R}^d$ is a bounded convex set, then K is of finite perimeter and $\nu_K(x) \in \mathcal{N}_K(x)$ for all $x \in \partial^* K \subseteq \partial K$, where, for each $x \in \partial K$, $\mathcal{N}_K(x) := \{\zeta \in \mathbb{R}^d : \zeta \cdot (x' - x) \leq 0 \forall x' \in K\}$ denotes the normal cone to K at x .

Energy

Let $\varphi : \mathbb{R}^d \rightarrow [0, +\infty)$ be a convex and positively homogeneous function of degree one that is bounded from below, i.e., there exists $c > 0$ such that

$$\varphi(\nu) \geq c \|\nu\| \text{ for all } \nu \in \mathbb{R}^d. \quad (2.1)$$

For a set of finite perimeter $E \subseteq H^+$, we define $F_{\lambda,\varphi}(E)$ as in (1.3). Given $v > 0$, we are interested in studying the shape of the solutions to (1.4).

REMARK 1. *Scaling* It is obvious that $F_{\lambda,\varphi}(rE) = r^{d-1}F_{\lambda,\varphi}(E)$ for any $r > 0$ and, in particular, the minimal energy $m_{\lambda,\varphi}(v) = \inf \{F_{\lambda,\varphi}(E) : |E| = v\}$ satisfies

$$m_{\lambda,\varphi}(v) = v^{\frac{d-1}{d}} m_{\lambda,\varphi}(1).$$

Wulff shape

In order to construct solutions to (1.4), we first define the *Wulff set* of φ , yet in a more general set-up: For any positively 1-homogeneous Borel function $\varphi: \mathbb{R}^d \rightarrow [0, +\infty)$ which is bounded from below (cf. (2.1)) but not necessarily continuous or even convex, we set

$$W_\varphi := \{x \in \mathbb{R}^d : \nu \cdot x \leq \varphi(\nu) \forall \nu \in \mathbb{S}^{n-1}\}.$$

In fact, for continuous φ , W_φ is the—up to translations unique—minimizer among sets with equal volume to the problem $E \mapsto \int_{\partial^* E} \varphi(\nu_E) d\mathcal{H}^{d-1}$ without substrate, cf. [9, 10, 18]. We recall some basic facts on Wulff sets.

PROPOSITION 2.

- (i) W_φ is a bounded, convex, and closed set with $0 \in \text{int } W_\varphi$.
- (ii) The convex conjugate φ^* is equal to the indicator function of W_φ , i.e., $\varphi^*(x) = 0$ if $x \in W_\varphi$ and $\varphi^*(x) = \infty$ if $x \notin W_\varphi$.
- (iii) For $x \in \partial W_\varphi$, we have that $\mathcal{N}_{W_\varphi}(x) = \partial\varphi^*(x)$, where $\partial\varphi^*(x)$ is the subgradient of φ^* at x .
- (iv) The Wulff shapes of φ and its convex envelope φ^{**} coincide: $W_\varphi = W_{\varphi^{**}}$.
- (v) If $x \in \partial W_\varphi$ and ζ lies in the normal cone to W_φ at x , then $x \cdot \zeta = \varphi^{**}(\zeta)$.

Proof. Convexity and closedness of W_φ , and the inclusions $0 \in B_c \subseteq W_\varphi$, for $c > 0$ given by (2.1), are immediate. Boundedness follows in our set-up from $-\varphi(-e_k) \leq x_k \leq \varphi(e_k)$ for $k = 1, \dots, d$ for any $x \in W_\varphi$. This proves (i). Now, (ii)–(v) are found in [9, propositions 3.4 & 3.5]. A careful inspection of the proofs in [9] reveals that the relevant assertions do not need continuity of φ (which is assumed there). The statement in (v) follows since, by (iii), $\zeta \in \partial\varphi^*(x)$, whence the Fenchel–Young identity implies $x \cdot \zeta = \varphi^*(x) + \varphi^{**}(\zeta)$ and so $x \cdot \zeta = \varphi^{**}(\zeta)$ by (ii). \square

Winterbottom shape

We now return to our convex, positively 1-homogeneous and bounded from below φ and set

$$W_{\lambda,\varphi} = W_\varphi \cap \{x \in \mathbb{R}^d : x_d \geq -\lambda\}.$$

If $|W_{\lambda,\varphi}| > 0$, the *Winterbottom set* with volume $v > 0$ is then defined as

$$W_{\lambda,\varphi}(v) = \left(\frac{v}{|W_{\lambda,\varphi}|} \right)^{\frac{1}{d}} (W_{\lambda,\varphi} + \lambda e_d). \quad (2.2)$$

Minimizers

We here summarize the different regimes for λ :

- (i) *Complete drying*: $\lambda \geq \varphi(-e_d)$. In this case, $W_{\lambda,\varphi} = W_\varphi$. In [remark 4](#), we will see that minimizers to $F_{\lambda,\varphi}$ for a given volume are those of the unconstrained system without substrate.
- (ii) *Partial drying/wetting*: $\lambda \in (-\varphi(e_d), \varphi(-e_d))$. Here, we have $W_{\lambda,\varphi} \subsetneq W_\varphi$ as shown in [lemma 6](#). Minimality of the Winterbottom shape will be established in [theorem 3](#).
- (iii) *Complete wetting*: $\lambda \leq -\varphi(e_d)$. Here $W_{\lambda,\varphi} = \emptyset$. In [remark 4](#), we will see that solutions to (1.4) do not exist if $\lambda < -\varphi(e_d)$ as ‘wetting’ configurations that intersect large parts of H have arbitrarily small energy. Generically, there are no minimizers in the special case $\lambda = -\varphi(e_d)$ either, while here for particular φ (even non-unique) minimizers might exist.

The first main theorem is the following characterization of minimizers in the partial drying/wetting regime.

THEOREM 3 *Let $\lambda \in (-\varphi(e_d), \varphi(-e_d))$ and $v > 0$. Then*

$$F_{\lambda,\varphi}(W_{\lambda,\varphi}(v)) \leq F_{\lambda,\varphi}(E)$$

for all $E \subseteq H^+$ sets of finite perimeter such that $|E| = v$. Moreover, equality holds if and only if there exists $\tau \in H$ such that $|E \Delta (W_{\lambda,\varphi}(v) + \tau)| = 0$.

REMARK 4.

- (i) *Complete drying*: $\lambda \geq \varphi(-e_d)$. Comparison to the unconstrained case shows that E is a solution to (1.4) if and only if $|E \Delta (W_{\lambda,\varphi}(v) + \tau)| = 0$ (recall definition (2.2) of $W_{\lambda,\varphi}(v)$) for some $\tau \in H^+$ (if $\lambda > \varphi(-e_d)$ and $\mathcal{H}^{d-1}(\{x \in W_\varphi : x_d = -\varphi(-e_d)\}) > 0$), respectively, $\tau \in H^+ \cup H$ (if $\lambda = \varphi(-e_d)$ or $\mathcal{H}^{d-1}(\{x \in W_\varphi : x_d = -\varphi(-e_d)\}) = 0$).
- (ii) *Complete drying*: $\lambda \geq \varphi(-e_d)$. Comparison to the unconstrained case shows that E is a solution to (1.4) if and only if $|E \Delta (W_{\lambda,\varphi}(v) + \tau)| = 0$ (recall definition (2.2) of $W_{\lambda,\varphi}(v)$) for some translation vector τ such that $\tau \in H^+$ if $\lambda > \varphi(-e_d)$ and $\mathcal{H}^{d-1}(\{x \in W_\varphi : x_d = -\varphi(-e_d)\}) > 0$ and $\tau \in H^+ \cup H$ if instead $\lambda = \varphi(-e_d)$ or $\mathcal{H}^{d-1}(\{x \in W_\varphi : x_d = -\varphi(-e_d)\}) = 0$.
- (iii) *Complete drying and partial drying/partial wetting*: $\lambda > -\varphi(e_d)$. For every set of finite perimeter $E \subseteq H^+$, one has

$$\int_{\partial^* E \cap H^+} \varphi(\nu_E) d\mathcal{H}^{d-1} \geq \varphi \left(\int_{\partial^* E \cap H^+} \nu_E d\mathcal{H}^{d-1} \right) = \mathcal{H}^{d-1}(\partial^* E \cap H) \varphi(e_d), \quad (2.3)$$

where we have used Jensen's inequality, the homogeneity of φ and the fact that, by the Gauss–Green Theorem for sets of finite perimeter, $\int_{\partial^* E} \nu_E \, d\mathcal{H}^{d-1} = 0$. This shows that $m_{\lambda,\varphi}$ (cf. [remark 1](#)) is positive if $\lambda > -\varphi(e_d)$.

- (iv) *Complete wetting*: $\lambda \leq -\varphi(e_d)$. In the case $\lambda < -\varphi(e_d)$, one may consider cylindrical sets $E_R = (0, R)^{d-1} \times (0, v/R^{d-1})$ with $R \rightarrow \infty$ to see that $m_{\lambda,\varphi} = -\infty$. In particular, solutions to (1.4) do not exist. In the case $\lambda = -\varphi(e_d)$, the admissible configurations E_R show that $m_{\lambda,\varphi} \leq 0$. Together with (2.3), this implies that $m_{\lambda,\varphi} = 0$. However, in this case, both existence and non-existence of minimizers might occur: If, e.g., φ is strictly convex, the above argument shows that $F_{\lambda,\varphi}(E) > 0$ for $|E| > 0$. If, instead, φ is affine near e_d the above computation shows that for a spherical cap $C_\varepsilon = \{x \in B_1(0) : x_d \geq 1 - \varepsilon\}$, $0 < \varepsilon \ll 1$, the set $E = \frac{v}{|C_\varepsilon|}(C_\varepsilon - (1 - \varepsilon)e_d)$ has $F_{\lambda,\varphi}(E) = 0$.
- (v) *Young's law*: The relation (1.6) can be seen as follows. Let $x \in \partial W_{\lambda,\varphi}$ with $x_d = -\lambda$ and $\nu(x) \in \mathcal{N}_{W_\varphi}(x)$. Then [proposition 2](#)(iii) and the Fenchel–Young identity imply $x \in \partial\varphi^{**}(\nu(x)) = \partial\varphi(\nu(x))$. For smooth φ , this shows that $\nabla\varphi(\nu(x)) = x$ and, hence,

$$\nabla\varphi(\nu(x)) \cdot (-e_d) = -x_d = \lambda.$$

Furthermore, we are able to establish the stability of the Winterbottom shape improving [theorem 3](#). This is formulated in our second main theorem.

THEOREM 5 *Let $\lambda \in (-\varphi(e_d), \varphi(-e_d))$ and $v > 0$. There is a constant $C > 0$ such that for every set $E \subseteq H^+$ of finite perimeter with $|E| = v$ there exists $\tau \in H$ that verifies*

$$\frac{|E \Delta (W_{\lambda,\varphi}(v) + \tau)|^2}{v^2} \leq C \left(\frac{F_{\lambda,\varphi}(E) - F_{\lambda,\varphi}(W_{\lambda,\varphi}(v))}{F_{\lambda,\varphi}(W_{\lambda,\varphi}(v))} \right).$$

3. Proof of the main theorems

In this section, we prove [theorems 3](#) and [5](#). In the following, we will make use of various unconstrained auxiliary functionals. If $\psi: \mathbb{R}^d \rightarrow \mathbb{R}$ is a homogeneous function of degree one (not necessarily convex or bounded from below), for a set $E \subseteq H^+$ of finite perimeter, we define

$$P_\psi(E) = \int_{\partial^* E} \psi(\nu) \, d\mathcal{H}^{d-1}.$$

Now define $\varphi_\lambda: \mathbb{R}^d \rightarrow \mathbb{R}$ as

$$\varphi_\lambda(\nu) = \begin{cases} \lambda t & \text{if } \nu = -te_d \text{ with } t > 0, \\ \varphi(\nu) & \text{otherwise.} \end{cases}$$

LEMMA 6. Let $-\varphi(e_d) < \lambda < \varphi(-e_d)$. Then,

$$P_{\varphi_\lambda}(E) \leq F_{\lambda,\varphi}(E)$$

for all sets of finite perimeter $E \subseteq H^+$, with equality if and only if

$$\mathcal{H}^{d-1}(\{x \in \partial^* E : \nu_E(x) = -e_d\} \setminus H) = 0.$$

In particular, $W_{\lambda,\varphi}(1) \subsetneq W_\varphi(1)$ and

$$P_{\varphi_\lambda}(W_{\lambda,\varphi}(1)) = F_{\lambda,\varphi}(W_{\lambda,\varphi}(1)).$$

Proof. The first two statements are direct consequence of the definition of P_{φ_λ} . As $W_{\lambda,\varphi}(1)$ is convex and $W_{\lambda,\varphi}(1) \subseteq \{x_d \geq 0\}$, it suffices to show that $W_{\lambda,\varphi}(1) \cap H \neq \emptyset$, or equivalently $W_\varphi \cap \{x_d = -\lambda\} \neq \emptyset$. In fact, if there exists $x \in \partial W_{\lambda,\varphi}(1)$ such that $x_d > 0$ and $-e_d = \nu(x) \in \mathcal{N}_{W_{\lambda,\varphi}(1)}(x)$, then

$$\begin{aligned} -x_d &= x \cdot (-e_d) \geq y \cdot (-e_d) = -y_d \quad \forall y \in W_{\lambda,\varphi}(1) \\ \iff y_d &\geq x_d > 0 \quad \forall y \in W_{\lambda,\varphi}(1). \end{aligned}$$

This contradicts $W_{\lambda,\varphi}(1) \cap H \neq \emptyset$. In order to see that $W_\varphi \cap \{x_d = -\lambda\} \neq \emptyset$, we choose $x_+, x_- \in W_\varphi$ such that $\pm e_d \in \mathcal{N}_{W_\varphi}(x_\pm)$. Then, by [proposition 2\(v\)](#), we have that $(x_\pm)_d = \pm x_\pm \cdot (\pm e_d) = \pm \varphi(\pm e_d)$. Thus by convexity of W_φ , there exists $x \in W_\varphi$ such that $x_d = -\lambda$. \square

LEMMA 7. Let $0 < \lambda < \varphi(-e_d)$. Then

$$P_{\varphi_\lambda^*}(W_{\lambda,\varphi}(1)) = P_{\varphi_\lambda}(W_{\lambda,\varphi}(1)) \leq P_{\varphi_\lambda}(E)$$

for all sets of finite perimeter $E \subseteq H^+$ such that $|E| = 1$. Moreover, equality holds if and only if there exists $\tau \in H^+ \cup H$ such that $|E \Delta (W_{\lambda,\varphi}(1) + \tau)| = 0$.

Proof. [lemma 7](#). First note that the argument in the proof of [lemma 6](#) shows that for $x \in \partial^* W_{\lambda,\varphi}$

$$\nu_{W_{\lambda,\varphi}}(x) = \begin{cases} \nu_{W_\varphi}(x) \neq -e_d & \text{if } x_d > -\lambda, \\ -e_d & \text{if } x_d = -\lambda. \end{cases} \quad (3.1)$$

Since $0 < \lambda < \varphi(-e_d)$, we have that φ_λ is bounded from below and that $W_{\lambda,\varphi} = W_{\varphi_\lambda}$ is the Wulff set of φ_λ . By [proposition 2\(iv\)](#), we therefore have

$$W_{\lambda,\varphi} = W_{\varphi_\lambda^{**}}. \quad (3.2)$$

Let $x \in \partial^* W_{\lambda,\varphi} = \partial^* W_{\varphi_\lambda^{**}}$. If $x_d > -\lambda$, we apply [proposition 2\(v\)](#) to both φ_λ^{**} and φ and get

$$\varphi_\lambda^{**}(\nu_{W_{\lambda,\varphi}}(x)) = x \cdot \nu_{W_{\lambda,\varphi}}(x) = \varphi(\nu_{W_{\lambda,\varphi}}(x)) = \varphi_\lambda(\nu_{W_{\lambda,\varphi}}(x)),$$

by (3.1). If $x_d = -\lambda$, we apply proposition 2(v) to φ_λ^{**} and use (3.1) to obtain

$$\varphi_\lambda^{**}(\nu_{W_{\lambda,\varphi}}(x)) = x \cdot (-e_d) = \lambda = \varphi_\lambda(\nu_{W_{\lambda,\varphi}}(x)),$$

too. It follows that

$$P_{\varphi_\lambda^{**}}(W_{\lambda,\varphi}) = P_{\varphi_\lambda}(W_{\lambda,\varphi}). \quad (3.3)$$

We can now conclude by referring to known results [9, 10, 18] on the unconstrained functional $P_{\varphi_\lambda^{**}}$ as, by (3.3) and (3.2), for any set $E \subseteq H^+$ of finite perimeter with $|E| = 1$ we have

$$P_{\varphi_\lambda}(W_{\lambda,\varphi}(1)) = P_{\varphi_\lambda^{**}}(W_{\lambda,\varphi}(1)) = P_{\varphi_\lambda^{**}}(|W_{\varphi_\lambda^{**}}|^{-1/d} W_{\varphi_\lambda^{**}}) \leq P_{\varphi_\lambda^{**}}(E) \leq P_{\varphi_\lambda}(E),$$

with equality only if $E = W_{\lambda,\varphi}(1) + \tau$ with $\tau \in H^+ \cup H$. \square

The following change of coordinates allows us to reduce to the case $\lambda > 0$. Given $x_0 \in \text{int}(W_\varphi)$, we define

$$\varphi_{x_0}(\nu) = \varphi(\nu) - x_0 \cdot \nu.$$

LEMMA 8. *Let $-\varphi(e_d) < \lambda < \varphi(-e_d)$. For all $x_0 \in \text{int}(W_\varphi)$, there exists $\varepsilon = \varepsilon(x_0) > 0$ such that*

$$\varphi_{x_0}(\nu) \geq \varepsilon \|\nu\| \quad \text{for all } \nu \in \mathbb{R}^d. \quad (3.4)$$

Furthermore, there exists $x_0 \in \text{int}(W_\varphi)$ such that for $\lambda' = \lambda + x_0 \cdot e_d$ we have that

$$(i) \ 0 < \lambda' < \varphi_{x_0}(-e_d) \quad \text{and} \quad (ii) \ P_{(\varphi_{x_0})_{\lambda'}}(E) = P_{\varphi_\lambda}(E). \quad (3.5)$$

In addition, we have

$$(i) \ x \in W_\varphi \iff x - x_0 \in W_{\varphi_{x_0}} \quad \text{and} \quad (ii) \ W_{\lambda',\varphi_{x_0}}(1) = W_{\lambda,\varphi}(1) + \tau \quad (3.6)$$

for $\tau = |W_{\lambda,\varphi}|^{-1/d}(-x_0 + (x_0 \cdot e_d)e_d) \in H$.

Proof. We first prove (3.4). As φ_{x_0} is positively 1-homogeneous, it suffices to prove the claim for $\nu \in \mathbb{S}^{d-1}$. By construction of W_φ for all $x \in W_\varphi$, we have $x \cdot \nu \leq \varphi(\nu)$ and hence

$$(x - x_0) \cdot \nu \leq \varphi(\nu) - x_0 \cdot \nu = \varphi_{x_0}(\nu) \quad \text{for all } \nu \in \mathbb{S}^{d-1}.$$

Since $x_0 \in \text{int}(W_\varphi)$, there is $\varepsilon > 0$ such that $\overline{B}_\varepsilon(x_0) \subseteq W_\varphi$ and thus choosing $x_{\varepsilon,\nu} = x_0 + \varepsilon\nu \in \overline{B}_\varepsilon(x_0)$ we find

$$\varepsilon = (x_{\varepsilon,\nu} - x_0) \cdot \nu \leq \varphi_{x_0}(\nu) \quad \text{for all } \nu \in \mathbb{S}^{d-1}.$$

This shows (3.4). Next, we prove (3.5)(i). To see this, observe

$$0 < \lambda' < \varphi_{x_0}(-e_d) \iff -x_0 \cdot e_d < \lambda < \varphi(-e_d).$$

By assumption, $\lambda < \varphi(-e_d)$. By choosing an element \bar{x} with maximal last component in the compact set W_φ and observing that $e_d \in \mathcal{N}_{W_\varphi}(\bar{x})$, with the help of

proposition 2(v), we also get

$$-\max\{x_0 \cdot e_d : x_0 \in W_\varphi\} = -\bar{x} \cdot e_d = -\varphi(e_d).$$

Since $\lambda > -\varphi(e_d)$, there exists $x_0 \in \text{int}(W_\varphi)$ such that $-x_0 \cdot e_d < \lambda$, too, as claimed. Next, we show (3.5)(ii). To this end, note that $(\varphi_{x_0})_{\lambda'}(\nu) = \varphi_\lambda(\nu) - x_0 \cdot \nu$ for all $\nu \in \mathbb{S}^{d-1}$ since

$$(\varphi_{x_0})_{\lambda'}(\nu) = \begin{cases} \varphi_{x_0}(\nu) &= \varphi(\nu) - x_0 \cdot \nu &= \varphi_\lambda(\nu) - x_0 \cdot \nu &\text{if } \nu \neq -e_d, \\ \lambda' &= \lambda - x_0 \cdot (-e_d) &= \varphi_\lambda(\nu) - x_0 \cdot \nu &\text{if } \nu = -e_d. \end{cases}$$

Now, by the Gauss–Green Theorem for sets of finite perimeter, for E a set of finite perimeter, we obtain

$$\begin{aligned} P_{(\varphi_{x_0})_{\lambda'}}(E) &= \int_{\partial^* E} (\varphi_{x_0})_{\lambda'}(\nu) \, d\mathcal{H}^{d-1} = \int_{\partial^* E} \varphi_\lambda(\nu) - x_0 \cdot \nu \, d\mathcal{H}^{d-1} \\ &= \int_{\partial^* E} \varphi_\lambda(\nu) \, d\mathcal{H}^{d-1} - \int_E \text{div}(x_0) \, dx = \int_{\partial^* E} \varphi_\lambda(\nu) \, d\mathcal{H}^{d-1} = P_{\varphi_\lambda}(E), \end{aligned}$$

where we used that $\text{div}(x_0) = 0$. To see (3.6)(i), it suffices to note that

$$\begin{aligned} x \in W_\varphi &\iff x \cdot \nu \leq \varphi(\nu) \quad \forall \nu \in \mathbb{S}^{d-1} \\ &\iff (x - x_0) \cdot \nu \leq \varphi(\nu) - x_0 \cdot \nu \quad \forall \nu \in \mathbb{S}^{d-1} \\ &\iff (x - x_0) \cdot \nu \leq \varphi_{x_0}(\nu) \quad \forall \nu \in \mathbb{S}^{d-1} \iff x - x_0 \in W_{\varphi_{x_0}}. \end{aligned}$$

In order to prove (3.6)(ii), note that

$$\begin{aligned} W_{\lambda', \varphi_{x_0}} &= \{x \in W_{\varphi_{x_0}} : x_d \geq -\lambda'\} = \{x \in W_{\varphi_{x_0}} : x_d \geq -\lambda - x_0 \cdot e_d\} \\ &= \{x \in W_\varphi - x_0 : (x + x_0)_d \geq -\lambda\} \\ &= \{x \in W_\varphi : x_d \geq -\lambda\} - x_0 = W_{\lambda, \varphi} - x_0. \end{aligned}$$

Therefore,

$$\begin{aligned} W_{\lambda', \varphi_{x_0}}(1) &= |W_{\lambda', \varphi_{x_0}}|^{-1/d} (W_{\lambda', \varphi_{x_0}} + \lambda' e_d) \\ &= |W_{\lambda, \varphi}|^{-1/d} (W_{\lambda, \varphi} - x_0 + (\lambda + x_0 \cdot e_d) e_d) \\ &= |W_{\lambda, \varphi}|^{-1/d} (W_{\lambda, \varphi} + \lambda e_d - x_0 + (x_0 \cdot e_d) e_d) = W_{\lambda, \varphi}(1) + \tau, \end{aligned}$$

where

$$\tau = |W_{\lambda, \varphi}|^{-1/d} (-x_0 + (x_0 \cdot e_d) e_d) \in H. \quad (3.7)$$

□

We are now in position to prove the main theorems.

Proof. Proof of theorem 3. By remark 1, it suffices to prove the theorem only for $v = 1$. To this end, let $E \subseteq H^+$ be such that $|E| = 1$. We choose $x_0 \in \text{int}(W_\varphi)$

and $\lambda' = \lambda + x_0 \cdot e_d$ such that the assertions of lemma 8 hold true. Using lemma 6, (3.5)(ii), and (3.6)(ii), we obtain

$$F_{\lambda,\varphi}(W_{\lambda,\varphi}(1)) = P_{\varphi_\lambda}(W_{\lambda,\varphi}(1)) = P_{\varphi_\lambda}(W_{\lambda',\varphi_{x_0}}(1)) = P_{(\varphi_{x_0})_{\lambda'}}(W_{\lambda',\varphi_{x_0}}(1))$$

and, for any set E of finite perimeter,

$$F_{\lambda,\varphi}(E) \geq P_{\varphi_\lambda}(E) = P_{(\varphi_{x_0})_{\lambda'}}(E).$$

Finally applying lemma 7 to φ_{x_0} and the positive λ' gives $P_{(\varphi_{x_0})_{\lambda'}}(W_{\lambda',\varphi_{x_0}}(1)) \leq P_{(\varphi_{x_0})_{\lambda'}}(E)$ if $|E| = 1$, and we have shown that

$$F_{\lambda,\varphi}(W_{\lambda,\varphi}(1)) \leq F_{\lambda,\varphi}(E)$$

for such E . In case of equality, we also have $P_{(\varphi_{x_0})_{\lambda'}}(W_{\lambda',\varphi_{x_0}}(1)) = P_{(\varphi_{x_0})_{\lambda'}}(E)$ and lemma 7 implies $E = W_{\lambda',\varphi_{x_0}}(1) + \tau' = W_{\lambda,\varphi}(1) + \tau + \tau'$ for τ as in (3.7) and some $\tau' \in H^+ \cup H$. As also $P_{\varphi_\lambda}(E) = F_{\lambda,\varphi}(E)$, necessarily $\tau + \tau' \in H$. This concludes the proof. \square

We are now in position to prove theorem 5 establishing the stability of the Winterbottom shape.

Proof. theorem 5. Let $x_0 \in \text{int}(W_\varphi)$ and $\lambda' = \lambda + x_0 \cdot e_d$ be such that the assertions of lemma 8 hold true. By properly rescaling, we may without loss of generality assume $|E| = 1$. In the following, we set $W = W_{\lambda,\varphi}(1)$ and $W' = W_{\lambda',\varphi_{x_0}}(1)$. We first want to prove that there exists $\tau \in \mathbb{R}^d$ such that

$$|E\Delta(W + \tau)|^2 \leq C(F_{\lambda,\varphi}(E) - F_{\lambda,\varphi}(W)). \quad (3.8)$$

The quantitative isoperimetric inequality [8, theorem 1.1] for the unconstrained functional $P_{(\varphi_{x_0})_{\lambda'}}^{**}$ yields $C > 0$ such that for a suitable $\tau' \in \mathbb{R}^d$ we have

$$|E\Delta(W' + \tau')|^2 \leq C \left(P_{(\varphi_{x_0})_{\lambda'}}^{**}(E) - P_{(\varphi_{x_0})_{\lambda'}}^{**}(W') \right).$$

Recalling that, by (3.6)(ii), there holds $W = W' + \hat{\tau}$ for some $\hat{\tau} \in H$ and setting $\tau = \tau' - \hat{\tau}$, we obtain

$$|E\Delta(W + \tau)|^2 = |E\Delta(W' + \tau')|^2 \leq C \left(P_{(\varphi_{x_0})_{\lambda'}}^{**}(E) - P_{(\varphi_{x_0})_{\lambda'}}^{**}(W') \right). \quad (3.9)$$

Now, by lemma 6, lemma 8, and, as $\lambda' > 0$, by lemma 7, we have

$$P_{(\varphi_{x_0})_{\lambda'}}^{**}(E) \leq P_{(\varphi_{x_0})_{\lambda'}}(E) = P_{\varphi_\lambda}(E) \leq F_{\lambda,\varphi}(E)$$

and

$$P_{(\varphi_{x_0})_{\lambda'}}^{**}(W') = P_{(\varphi_{x_0})_{\lambda'}}(W') = P_{\varphi_\lambda}(W') = P_{\varphi_\lambda}(W) = F_{\lambda,\varphi}(W),$$

where we again used that $W = W' + \hat{\tau}$ with $\hat{\tau} \in H$. Therefore

$$P_{(\varphi_{x_0})_{\lambda'}^{**}}(E) - P_{(\varphi_{x_0})_{\lambda'}^{**}}(W') \leq F_{\lambda, \varphi}(E) - F_{\lambda, \varphi}(W).$$

Together with (3.9), this yields (3.8).

The challenge that remains is to show that τ can be chosen in H , i.e., such that $\tau_d = 0$. In order to do that, we distinguish some cases.

CASE 1. Assume (3.8) holds true with $\tau_d < 0$. By convexity of W , we have

$$|E\Delta(W + \tau)| \geq |\{x \in \tau + W : x_d < 0\}| = |\{x \in W : x_d < -\tau_d\}| \geq c \min\{-\tau_d, 1\}$$

for a constant $c > 0$. Since also

$$|(W + \tau)\Delta(W + \tau - \tau_d e_d)| \leq C \min\{-\tau_d, 1\}$$

(note that trivially $|(W + \tau)\Delta(W + \tau - \tau_d e_d)| \leq 2|W| \leq C$), we find that

$$\begin{aligned} |E\Delta(W + \tau - \tau_d e_d)| &\leq |E\Delta(W + \tau)| + |(W + \tau)\Delta(W + \tau - \tau_d e_d)| \\ &= (1 + Cc^{-1})|E\Delta(W + \tau)|. \end{aligned}$$

This implies the claim in view of (3.8).

CASE 2. Assume (3.8) holds true with $\tau_d > 0$. In the following, we denote by

$$W_\varphi(v) = \left(\frac{v}{|W_\varphi|} \right)^{\frac{1}{d}} W_\varphi$$

the rescaled Wulff set of φ with volume $v > 0$. Since in the partial drying/wetting regime $W_\varphi(1)$ (placed in H^+) is not optimal for $F_{\lambda, \varphi}$, we have $P_\varphi(W_\varphi(1)) > F_{\lambda, \varphi}(W_{\lambda, \varphi}(1))$. We can thus define a positive constant c_0 by asking that

$$(1 - c_0)^{\frac{d-1}{d}} P_\varphi(W_\varphi(1)) - (\varphi(e_d) + \varphi(-e_d))c_0 = F_{\lambda, \varphi}(W_{\lambda, \varphi}(1)) + \delta,$$

where $\delta := \frac{1}{2}(P_\varphi(W_\varphi(1)) - F_{\lambda, \varphi}(W_{\lambda, \varphi}(1))) > 0$.

CASE 2A. Suppose that $|\{x \in E : x_d < \tau_d\}| \geq c_0 \min\{\tau_d, 1\}$. Then

$$|E\Delta(W + \tau)| \geq c_0 \min\{\tau_d, 1\}$$

and, similarly as above, from

$$|(W + \tau)\Delta(W + \tau - \tau_d e_d)| \leq C \min\{\tau_d, 1\},$$

we conclude

$$\begin{aligned} |E\Delta(W + \tau - \tau_d e_d)| &\leq |E\Delta(W + \tau)| + |(W + \tau)\Delta(W + \tau - \tau_d e_d)| \\ &= (1 + Cc_0^{-1})|E\Delta(W + \tau)|. \end{aligned}$$

Again this concludes the proof with the help of (3.8).

CASE 2B. Assume that $|\{x \in E : x_d < \tau_d\}| < c_0 \min\{\tau_d, 1\}$. Then there is an $\varepsilon \in (0, \tau_d)$ such that

$$\mathcal{H}^{d-1}(E \cap (\varepsilon e_d + H)) \leq c_0 \min\{1, \tau_d^{-1}\}.$$

We cut along this hyperplane and set $\tilde{E} = \{x \in E : x_d > \varepsilon\}$. With this set, we then get

$$F_{\lambda, \varphi}(E) \geq F_{\lambda, \varphi}(E \setminus \tilde{E}) + P_{\varphi}(\tilde{E}) - (\varphi(e_d) + \varphi(-e_d))\mathcal{H}^{d-1}(E \cap (\varepsilon e_d + H)).$$

By [remark 4\(iii\)](#), the first term on the right hand side is non-negative and we get the bound

$$\begin{aligned} F_{\lambda, \varphi}(E) &\geq P_{\varphi}(\tilde{E}) - (\varphi(e_d) + \varphi(-e_d))c_0 \min\{1, \tau_d^{-1}\} \\ &\geq P_{\varphi}(W_{\varphi}(|\tilde{E}|)) - (\varphi(e_d) + \varphi(-e_d))c_0 \\ &= |\tilde{E}|^{\frac{d-1}{d}} P_{\varphi}(W_{\varphi}(1)) - (\varphi(e_d) + \varphi(-e_d))c_0, \end{aligned}$$

where in the second step we have used that the Wulff shape $W_{\varphi}(|\tilde{E}|)$ minimizes the unconstrained functional P_{φ} among sets of volume $|\tilde{E}|$. As by assumption $|\tilde{E}| \geq 1 - c_0$, it follows that

$$F_{\lambda, \varphi}(E) \geq (1 - c_0)^{\frac{d-1}{d}} P_{\varphi}(W_{\varphi}(1)) - (\varphi(e_d) + \varphi(-e_d))c_0 \geq F_{\lambda, \varphi}(W_{\lambda, \varphi}(1)) + \delta \quad (3.10)$$

by our choice of c_0 . Thus, for any $C \geq 4\delta^{-1}$, we have even for $\tau = 0$

$$|E \Delta W|^2 \leq (|E| + |W|)^2 = 4 \leq C(F_{\lambda, \varphi}(E) - F_{\lambda, \varphi}(W)).$$

□

Acknowledgements

The research of LK was supported by the DFG through the Emmy Noether Programme (project number 509436910).

References

- [1] L. Ambrosio, N. Fusco, and D. Pallara. *Functions of bounded variation and free discontinuity problems* (Oxford: Oxford University Press, 2000).
- [2] T. Bonnesen. Sur une amélioration de l'inégalité isopérimétrique du cercle et la démonstration d'une inégalité de Minkowski. *C. R. Acad. Sci. Paris* **172** (1921), 1087–1089.
- [3] M. Cicalese and G. P. Leonardi. Selection principle for the sharp quantitative isoperimetric inequality. *Arch. Ration. Mech. Anal. (2)* **206** (2012), 617–643.
- [4] E. Davoli and P. Piovano. Analytical validation of the Young-Dupré law for epitaxially-strained thin films. *Math. Models Methods Appl. Sci. (12)* **29** (2019), 2183–2223.
- [5] G. De Philippis and F. Maggi. Regularity of free boundaries in anisotropic capillarity problems and the validity of Young's law. *Arch. Ration. Mech. Anal. (2)* **216** (2015), 473–568.
- [6] A. Dinghas. Über einen geometrischen Satz von Wulff für die Gleichgewichtsform von Kristallen. *Z. Kristallogr. Cryst. Mater. (1–6)* **105** (1944), 304–314.

- [7] L. C. Evans and R. F. Gariepy. *Measure theory and fine properties of functions* (CRC Press, Boca Raton, London, New York, Washington, DC, 1992).
- [8] A. Figalli, F. Maggi and A. Pratelli. A mass transportation approach to quantitative isoperimetric inequalities. *Invent. Math. (1)* **182** (2010), 167–211.
- [9] I. Fonseca. The Wulff theorem revisited. *Proc. R. Soc. Lond. A (1884)* **432** (1991), 125–145.
- [10] I. Fonseca and S. Müller. A uniqueness proof for the Wulff theorem. *Proc. R. Soc. Edinb. A (1–2)*, **119** (1991), 125–136.
- [11] N. Fusco, F. Maggi and A. Pratelli. The sharp quantitative isoperimetric inequality. *Ann. Math. (3)* **168** (2008), 941–980.
- [12] C. Herring. Some theorems on the free energies of crystal surfaces. *Phys. Rev. (1)* **82** (1951), 87–93.
- [13] S. Kholmatov. On the minimality of the Winterbottom shape (arXiv: [2402.02179](https://arxiv.org/abs/2402.02179), 2024).
- [14] R. Kotecky and C. Pfister. Equilibrium shapes of crystals attached to walls. *J. Stat. Phys. (1)* **76** (1994), 419–446.
- [15] G. Pascale and M. Pozzetta. Quantitative isoperimetric inequalities for classical capillarity problems (arXiv: [2402.04675](https://arxiv.org/abs/2402.04675), 2024).
- [16] J. E. Taylor. Existence and structure of solutions to a class of nonelliptic variational problems. *Symp. Math.* **14** (1974), 499–508.
- [17] J. E. Taylor. Unique structure of solutions to a class of nonelliptic variational problems. *Proc. Symp. Pure Math.* **27** (1975), 419–427.
- [18] J. E. Taylor. Crystalline variational problems. *Bull. Am. Math. Soc. (4)* **84** (1978), 568–588.
- [19] W. L. Winterbottom. Equilibrium shape of a small particle in contact with a foreign substrate. *Acta Metall. (2)* **15** (1967), 303–310.
- [20] G. Wulff. Zur Frage der Geschwindigkeit des Wachstums und der Auflösung der Kristallflächen. *Z. Kristallogr.* **34** (1901), 449–530.
- [21] T. Young. An essay on the cohesion of fluids. *Phil. Trans. R. Soc.* **95** (1805), 65–87.